

building
to
learn

Hemcrete Tower

student project
pack



constructionarium

What is Hemcrete

Hemcrete, Hempcrete or Hemp Lime, is a novel construction material which can be thought of as a lightweight, low-strength concrete.



The principal constituent of Hemcrete is hemp shiv (also known as hurd), the woody core or pith of the hemp plant. This is combined with lime to form a fresh hemp lime mix which can then be placed and compacted inside formwork. Commonly hemcrete is formed into blocks or panels for use as a walling or roofing material.

Whilst hemcrete has a low compressive strength (0.2 – 1.0N/mm²), it has a number of advantages as a construction material:

- Its low thermal conductivity (0.10 – 0.30W/mK) means that it is a good insulant;
- It is both hygroscopic and permeable to water vapour, allowing wall construction which “breathes” and which naturally helps to condition the internal environment of the building it surrounds;
- It is lightweight, having a dry density (300 – 900 kg/m³ depending on mix and placement method)...

...but Hemcrete’s principal advantage is that it uses what is essentially a waste product from a fast-growing, industrial crop grown here in the UK and in so doing stores, or “sequesters”, atmospheric CO₂. For this reason Hemcrete is being promoted as a construction material which can be used to combat climate change.

Some examples of hemcrete being used in exemplar sustainable and “Zero Carbon” projects are shown below:




Orwell Housing Association’s Clayfields Housing – Suffolk UK



Adnam’s Distribution Centre, Southwold, Suffolk UK

The Hemcrete Tower

The proposal is to build a 3.5m diameter, 5.4m high hemcrete tower supported by a timber frame. Rather than creating a spiral staircase to nowhere, the tower will form a vantage point from which to take in the rest of the Constructionarium projects.

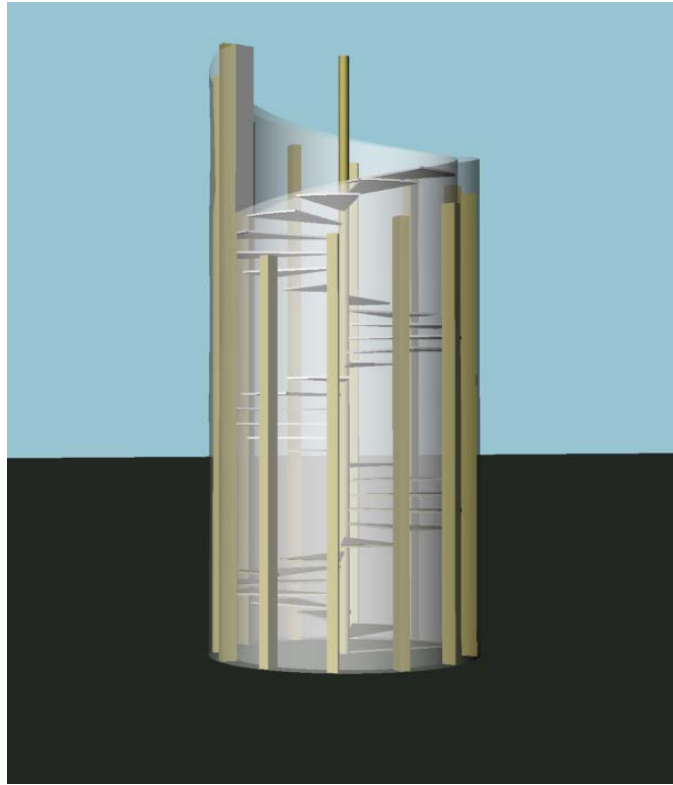


Early concept visualisation

The internal timber frame will contain a spiral stair providing access to a viewing platform at the top of the tower, and the structure will be topped-out with a timber pitched roof (note that the roof is not covered).

The internal spiral stair might be thought of as a timber variant of the classic stone "cantilever" spiral stair meets Jenga construction!



The "Tulip Stair" – Queen's House, Greenwich

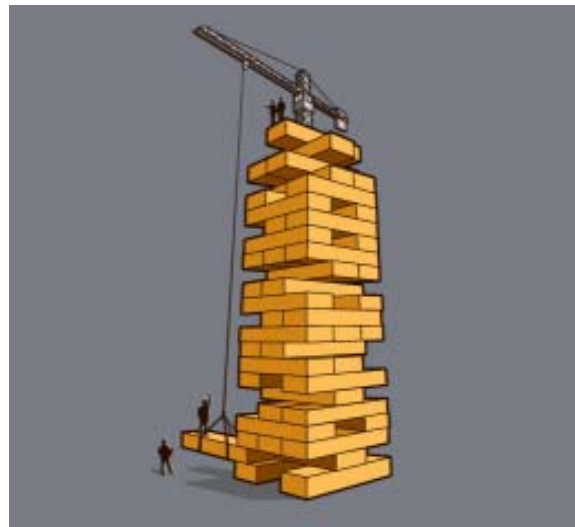

Jenga construction?

The spiral stair will be constructed in modular form from pre-fabricated timber tread assemblies.

The principal gravity load-bearing elements will be a series of vertical timber studs arranged in a radial formation around the perimeter of the tower.

Lateral and torsional stability of the tower will be provided for by shear panel action within a vertical cylindrical ply diaphragm acting together with the hemcrete perimeter wall (although a rather poor material from a structural point of view, hemcrete does have some racking resistance).

The tower will be founded on a lightly reinforced ground-bearing slab.

Good carpentry skills, careful setting-out and thorough consideration of the correct sequencing of the construction works will be essential to the success of the project, keeping in mind safety of workers at all time, speed of construction and budget.

Brief

Your brief is to construct the Hemcrete Tower over the Constructionarium week.

You will have to coordinate efficiently the erection of the timber frame, the construction of the hemcrete wall and mixing of the material, the erection of the roof, and the off-site fabrication and placing of the stair treads and top quarter landing.

Site layout at the start of the week

Your site is level. The ground-bearing concrete slab on which to found the tower might have been provided. If it has not been, you will have to integrate its construction to your program.

Plant and Equipment

You will have limited access to an excavator for the construction of your slab, and to a crane for lifting the roof members.

What you will have to do

- Create a GANTT chart of key activities and time for completion; determine the requirement for power tool training of operatives; meet daily with client's representative; submit method statements for approval by site manager; submit list of kit and equipment & plant requirements to store manager.
- Design the outer shuttering used for the construction of the wall,
- Set-out the stud plates, door opening and vertical timber posts on the foundation;
- Install noggins between vertical posts (ensuring verticality of timber posts at all times);
- Bend and fix inner ply diaphragm to timber posts;
- Fabricate and install stair tread assemblies in sequence finishing with the viewing platform;
- Batching and mixing of hemcrete;
- Install the outer temporary shutter as construction of the wall progresses;
- Fabricate and install the roof structure;
- **Construction of the tower will involve working at height. Safe access and egress must be considered at every stage of the construction to ensure a safe working environment;**
- **Stability of the overall structure must be maintained at all times and risk assessment methods statement report produced before each major construction activity commences.**

Friday feature

You will complete the building by removing the temporary external shutter that will finally unveil the hemcrete wall.

References

Hemp Lime Construction Products Association (HLCPA) website: <http://www.hemplime.org.uk>

Tradical website: <http://www.lhoist.co.uk/tradical/>

Limetech website: <http://www.limetechology.co.uk/>

A p p e n d i x

The following appendix presents the notes of the lecture *Building with Hemp and Lime* by Ranyl Rhydwen, lecturer at the Centre for Alternative Technology. These should give the student sufficient background information on the material.



Building with Hemp and Lime

By Ranyl Rhydwen, edited for Distance Learning by Damian Randle

This lecture investigates hemp and lime as a building material, in use, and covers the properties of lime, characteristics of hemp and lime construction, thermal performance, costs, and quantities, building issues, and then finally hempcrete specifically: CO₂ emissions and potential market.

In the book you will find the ‘sister piece’, ‘Hemp (Cannabis Sativa L.)’, which should be read in order to understand the historical, agricultural, environmental and economic background issues.

Lime

Lime has many environmental problems associated with it.

- It is mined on a large scale.
- It has a moderately high embodied energy (800kg / tonne).
- It is a finite resource.
- It is processed centrally away from the mining operations, necessitating the high haulage costs of a heavy material (heavy loads cause more CO₂ emissions and pollution)(WWF 1994).
- Lime Kilns use fossil fuels.
- It is associated with biodiversity loss due its mining operations and its contribution to global warming.

Despite this are many benefits to using lime. The following are the advantages of using lime as a plaster, render, and mortar in buildings;

1. It is “breathable” (high porosity, high water vapour permeability): breathable walls control internal humidity, reducing condensation and preventing mould growth. This improves the indoor air quality and the health of a building’s occupants.
2. Low thermal conductivity - $\sim 1 \text{ W}/(\text{m K})$ - and a moderately high specific heat allow the plaster to act effectively as a thermally massive heat store, contributing to the thermal comfort of the internal environment.
3. Lime is a long lasting material. (For example the Pantheon in Rome).
4. Lime is easily recyclable (re-burnt to form hydrated lime or used as aggregate) or is naturally absorbed into the land without causing toxicity.
5. Autogenous Healing: as lime buildings move small cracks can appear. Water penetrates into the cracks and dissolves any free lime. This brings it to the surface where the lime carbonates and heals the crack automatically.



6. Protection: lime acts as a very good ‘sacrificial’ external surface, protecting the essential structural elements of building from the weather, fire and vermin, although it must be maintained.
7. Lime mortars protect stone work and bricks, enabling them to be easily recycled, reduce material usage over time and lessen the need for major building repairs (Holmes and Wingate (2002), p..62).
8. Lime mixtures have good workability and are well suited for plastering.
9. Lime is alkaline, preventing mould growth and making it undesirable to small animals.
10. Lime washes are breathable and aesthetically appealing.
11. Lime allows for relatively easy building maintenance; regular lime washes or re-pointing prolong the longevity of a building.

Sources: May (1998), Holmes and Wingate (2002), Building with lime forums (2005), BRE (2001).

Lime is reasonably difficult to use in comparison cement and is more labour intensive. It requires patience to work with and careful site management to ensure the material sets properly. Lime requires several coats over several days, has to be cherished (kept moist) and protected from the weather for up to a week for successful application. It takes time for lime renders and plasters to fully set (several months) and it can be damaged by frost before becoming fully set (Holmes and Wingate (2002), p. 126) meaning that construction is weather dependent and external work is not recommended in the winter months. All of these considerations mean that lime has become unpopular in modern, fast, economically driven building sites where time is money (May 1998).

To minimize the environmental impact of lime, the smallest amount of lime possible should be used that maintains the benefits of using it outlined above. The carbon dioxide emissions, pollution, waste, haulage requirements and landscape disruption from mining would be vastly reduced if limestone could be mined and burnt locally in efficient kilns using biomass as fuel, as was traditionally the case in the UK (May 1998). Its CO₂ emissions per tonne can possibly be reduced from 880kg to 330kg. Overall it seems reasonable to advocate lime as a building material, from an environmental perspective, for all of the benefits outlined above. Further reasons are that it increases the longevity of buildings, improves the internal air quality and doesn’t require landfill and, if only lime was produced from limestone and not cement, it can be made using biomass.

Although burning biomass is CO₂ neutral it is still a finite resource as it needs available land to be grown. The dangers of the over production of lime from biomass are intensive monoculture farming and displacement of food crops. Emphasizing again that using as little lime as possible to do the job required is desirable.



Hemp and Lime Construction

Hemp hurds can be combined with lime to form the concrete like substance termed “Hempcrete”. This has been used in France since the early 1990’s to construct non-weight bearing insulating infill walls supported by a timber frame: see Figure 2. The walls are internally plastered and externally rendered with lime and finished with lime washes. The walls are also breathable, which controls moisture and condensation and improves internal air quality. The hempcrete is also used for floor slabs, ceiling insulation and as an internal coating for renovating old stone walls.

Hempcrete has a λ value (conductivity which the rate of the passage of heat through the material) of $\sim 0.076 - 0.11 \text{ W/(m.K)}$ when mixed with a mild to moderate hydraulic lime consisting of $\sim 85\%$ hydrated lime and $\sim 15\%$ clay or pozzolans. For floor slabs, a more hydraulic lime is used and sand is added to improve strength and water resistance λ value $\sim 0.13 \text{ W/(m.K)}$. For the ceiling insulation and the internally insulating stone wall coating, a pure hydrated lime is used and a higher percentage of hemp to provide a more insulating and lighter mixture $\lambda \sim 0.08 \text{ W/(m.K)}$.

There are several construction firms in France using the technique (e.g. Artcan, Camonose) and approximately 200-300 homes have been built. As lime has an embodied energy of $\sim 20\text{-}50\%$ lower than concrete and hemp is deemed environmental friendly with a low embodied energy, 1.4 MJ/tonne (BRE 2001, Pervaiz 2003), the main target is the environmental building sector.

This sector has grown in France and currently 20% of all the hemp hurds produced in France (~ 6000 tonnes a year) are utilised in the industry, an increase from only 5% in 1999 (IENICA 2003, IENICA 1999).

Two houses were built in the UK as part of the Haverhill housing project sponsored by Suffolk Housing Society in collaboration with BRE, who performed a full assessment of the building technique and the suitability of the material. The research was intended to investigate the use of the material covering several areas of concern:

- Relative structural, thermal, acoustic, permeability and durability qualities;
- Reduction in waste generated on site;
- Environmental impact;
- Construction costs (BRE 2001).

Hempcrete was used for the external (200mm, U-value $\sim 0.58 \text{ W m}^{-2} \text{ K}^{-1}$ (Ralph Carpenter Arch. Personal communication) and internal walls and to make a ground floor slab as detailed in the report. The reports main findings were that;

- *Structure & durability*: The qualities of hemp homes were found to be at least equal to those of traditional construction.



- *Thermal comparisons:* Heating fuel consumed by the hemp homes is no greater than that used in the traditionally constructed houses.
- *Acoustics test:* Hemp homes did not perform as well as the traditional houses but they did meet the sound resistance requirement.
- *Permeability:* Both forms of construction appear to give complete protection against water penetration. However, the hemp homes generate less condensation.
- *Waste minimisation:* There appears to be little difference in the amount of waste produced by each method. Although the waste is of a different nature in each case, both are likely to have an environmental impact (BRE 2001).

Thermal Performance

The thermal performance of the hemp homes was interesting as despite having higher U-values (Hemp homes 0.58 w/m².K Control Homes 0.35 w/m²/k) (U-values reflect how fast heat passes or is lost through a wall. The higher the value the faster heat is lost) they performed as well as the standard construction that met Part L 2002 UK regulations when the homes were occupied or unoccupied. The actual temperature maintained in the hemp homes tended to be 2°C higher than the standard homes in winter despite having virtually the same heating fuel consumption for the period (BRE 2001).

It was also found in a follow-up report using thermographic cameras that the external temperature of the hemp homes' walls was lower (~5°C) than for the standard construction homes despite the internal temperature being maintained at 20°C in both (BRE 2003). This second finding could imply that heat is flowing more readily through the standard wall construction despite its lower U-value, this could be a failure of the standard homes walls insulation (poor construction or becoming wet). The hemp homes also used less fuel to heat during the winter of 2002-3 (BRE 2003).

Another factor in the thermal performance of hempcrete walls is their thermal mass. Thermal mass will tend to absorb heat during hotter periods and release it again during colder periods. Thermal mass is not accounted for in U-values. Therefore the unexpected thermal performance seen in the hemp homes could in part be explained by the inherent thermal mass of the hemp walls acting as a heat capacitor. When DEFRA reported on hempcrete construction it recommended that the technique be taken up more widely, to provide buildings with thermal mass but low embodied energy (DEFRA 2005c).

Regarding concrete, it has been found that its thermal properties are dependent on the materials added, their proportions in the mixture, the amount of water used, the degree of porosity (air holes) and the final density (Bouguerra 1998, Kahn 2002, Demirbogia 2005, Mendes 2001). Figure 1 demonstrates the difference porosity and therefore density can make on conductivity. As concrete is 60% lime it seems reasonable to presume that the differing mixture parameters of hempcrete will have a similar affect on thermal properties.



“Because of the growth of interest in the use of hemp with lime..... A particular challenge to be addressed for wall systems relates to the increasing requirements of UK Building Regulations for thermal insulation. Although fibres in blocks or lime increase the insulation value, this is not going to be sufficient for the new ‘U’ values without very thick walls, and these are not likely to be acceptable. There is therefore a need to establish an effective solution to this challenge” (DEFRA 2005c).

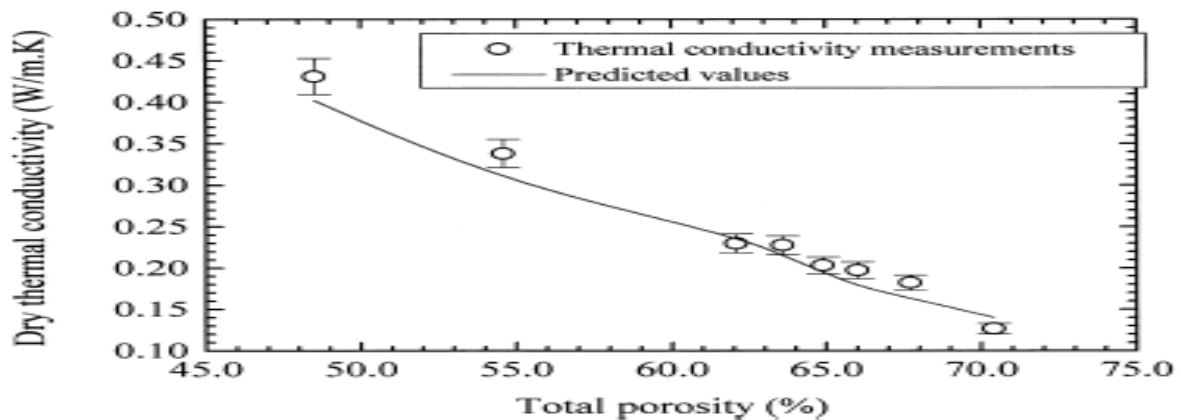


Figure 1: The effect of porosity. Source: Bouguerra (1998).

Apart from the inherent thermal properties of the hempcrete, other factors are likely to have helped to maintain the higher temperatures. Thermal bridging across a building’s framework can result in substantial heat losses. These are not a factor in hempcrete construction as the wooden frame is completely isolated by the mixture, meaning there is no thermal bridging. Hempcrete can also be easily formed up to window and door frames, creating air-tight seals preventing unwanted drafts and areas of heat loss. This is demonstrated in the thermal images made by BRE of the hemp homes where there are no heat losses seen around the windows and doors (BRE 2003). This also tends to suggest that the new building regulation requirements for air tightness are likely to be able to be achieved using hempcrete.

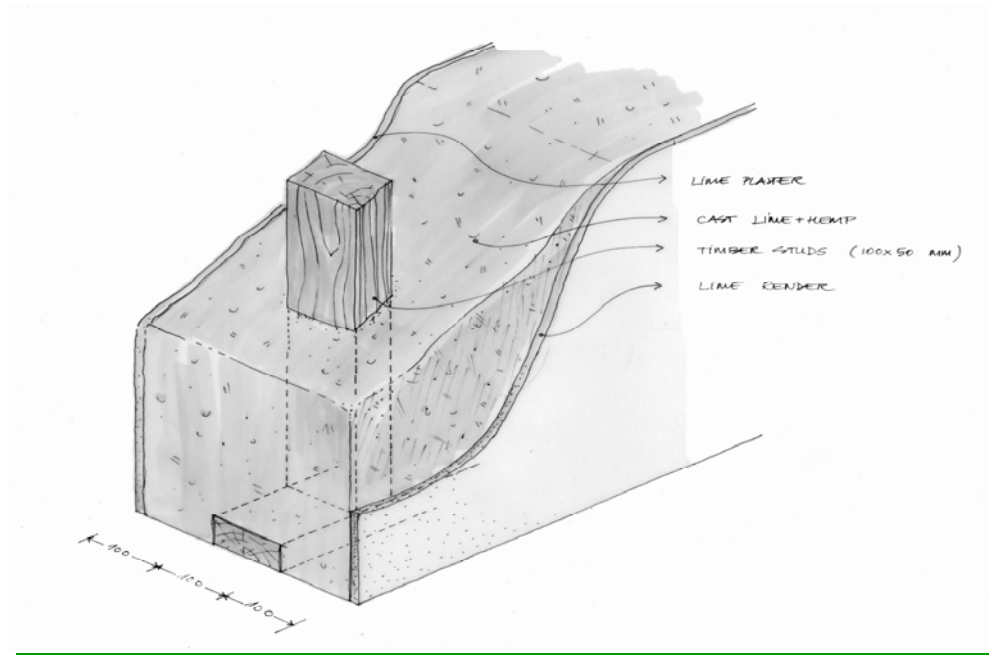


Figure 2: Hempcrete Wall. Source: Ian Pritchett (CAT 2006).

Construction Costs and Considerations

For Haverhill it was estimated that the true cost of building with hemp was £526 per square metre of floor and only £478 for a traditional style construction (BRE 2001). Labour costs to build the outside shell of the first hemp home consisted of 62% of the overall costs: this was reduced to 47% for the second home. For standard construction 57% of the cost is labour (BRE 2001). The two hemp houses were constructed without any prior training and the time of construction of the first house (~1100hrs) was considerably longer than for the second (~400hrs) (Construction time for the standard homes was ~400hrs).

The main reason cited for the reduction in construction time between the 2 hemp homes was that the builders had learnt how to use the material. It was also felt that the time taken for construction would fall further as experience grew (BRE 2001). It is clear that the time of construction can be reduced dramatically and the technique is considered to be relatively “easy” (Henry D O’Thompson Old Builder’s, Eire. CAT 2006). The material costs for the shell of the hemp homes were also 2 to 3 times more expensive than the standard build. However, at the time of writing the report, it was estimated that £1500 could be saved on the price of the lime (BRE 2001) and hemp can now be obtained more cheaply in the UK.

The price of the hemp walls in the Haverhill project was £194 per m². At the recent hemp conference at CAT in March 2006, Limetec’s Ian Pritchett estimated that currently a 300mm wall including render and plaster could be made for between £90-120 per m², which compares well to the standard construction costs of £140 per m², as in Haverhill. At the current cost of a bag of lime ~£7 and hemp at £7-8 per 200l bale, (2009) the cost of a m² of 300mm is ~300l of hemp and 3bags of lime;



~£33, labour costs on top are variable from very low (D.I.Y + volunteers) to very high (e.g. Industrial Contractor).

Amount of Materials

Presuming a thickness of 400mm (to achieve a U-value $<0.35 \text{ W m}^{-2} \text{ K}^{-1}$ and a wall area of 90 m^2 (the Haverhill homes were 86 m^2 and 106 m^2) the volume of hemp required to construct the walls of the house would be 36000 litres or 7200 kg as hemp weighs ~20kg per 100 litres. Presuming the floor area to be $\sim 40 \text{ m}^2$ at 100 mm depth this will require another 4 m^3 , 4000 litres or 800 kg of hemp. The average yield of hemp straw in the UK is approximately 5500 kg per hectare of which ~70% or 3850 kg are hurds. Thus it will take 8000 kg of hurds or ~2 hectares of hemp to supply enough hemp hurds for a 2 bed terrace with 400 mm walls. The depth of wall makes a substantial difference to the amount of hemp required see [Figure 3](#). Using as little lime as possible is also desirable from an environmental perspective, meaning wall thickness need to as low as possible to maintain performance.

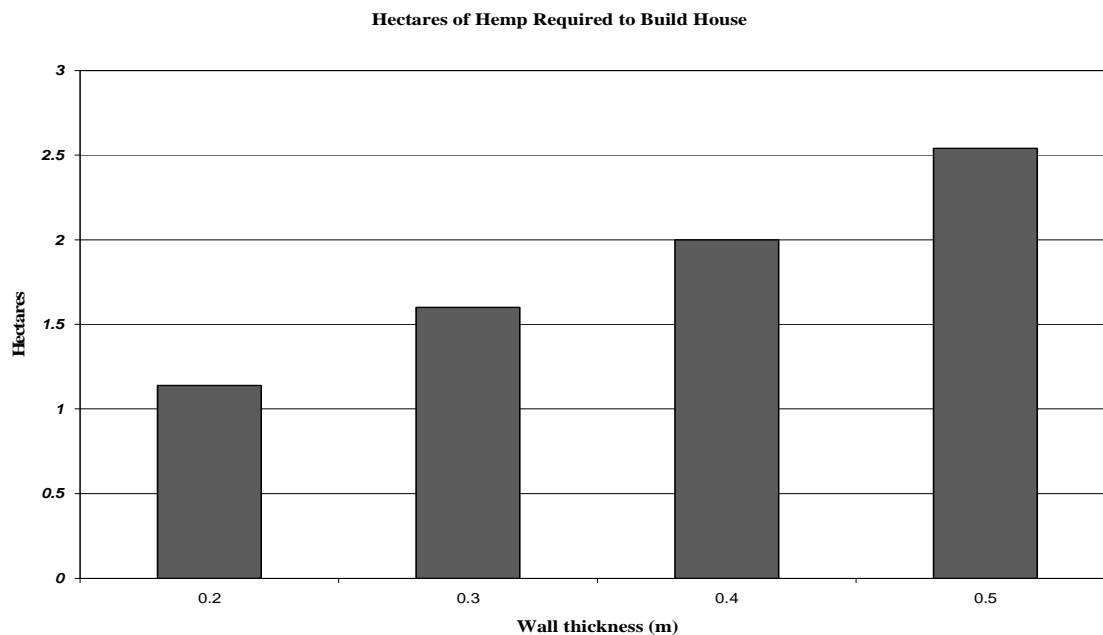


Figure 3: Area required against thickness of wall. Source: this author.

Building Issues:

The Haverhill report contains an extensive review of on-site problems encountered and basic recommendations. One of the main problems was the weather, which was mainly responsible for the build taking almost twice as long expected. Lime is sensitive to frost damage and therefore construction had to wait for the temperature to be above 5°C . It is also necessary to keep lime plastered and rendered walls moist for a short period (3-7days) after they have been applied and it takes approximately 2-3 months for the lime to completely dry.



The drying time is longer in cold and wet conditions. It was however estimated by Ian Pritchett at CAT (2006) that if the hempcrete is sprayed onto the wall (a technique already developed in France), full construction time can be as little as 2 weeks. The wet environment near the wall during the drying period can lead to mould growth on materials close to the wall (e.g. the back of picture frames) and on surface hemp which hasn't got an adequate covering of lime, but not in the actual wall, as lime's high pH prevents mould growth.

Henry O'Thompson reported incidences of mould occurring in this manner, although Ian Pritchett felt that this could be overcome by using a more hydraulic lime (Discourse CAT (2006)). Ralph Carpenter (personal communication) has noted that north and west walls seem to be more prone to this problem although once the mould is removed and the wall plastered the problems haven't reoccurred.

All these considerations led to the recommendation that the technique should only be considered between February and September in the UK (BRE 2001). This leads to a problem as hemp is harvested in September and therefore over-winter storage is necessary which increases prices and complicates logistics. It costs ~£30 a tonne to store hemp and as discussed takes up a lot of room due to its high bulk density. These issues are difficult and not being able to build all year round in the U.K. climate may be restrictive for the building industry to adopt the technique. Lime renders need continued maintenance as they are primarily a sacrificial layer to the weather to protect the underlying wall.

“However, the maintenance burden associated with hemp is regarded as comparatively small. As an in-situ material, repairs, minor alterations or remedial works are likely to be accommodated with comparative ease. Apparently, the material has been used extensively for “plaster” mouldings in houses across France” (BRE 2001).

The strength of the mixture was tested and *“the results of this test were a mean compressive failure strength of 0.458 MPa for the ‘wall’ mix and a compressive stress at 10% relative to deformation of 0.836MPa for the ‘floor’ mix. This suggests that the walling material will continue to deform as the load is applied but the flooring material is more rigid as a result of the sand/aggregate” (BRE 2001).* Although the waste produced for the hemp homes was reported to be the same as for standard construction, the waste was all fully recyclable. Furthermore, due to the weight of the walls, the hemp homes only required half the foundations and the material dug out for the foundations comprised 87% of the waste burden for building in general.

The hemp floor slab and walls were considered relatively impermeable to water which was confirmed by BRE in an extensive water saturation test which meant that the hemp homes didn't require any damp-proof course (BRE 2001). It was also considered that the hemp homes had less condensation, as would be expected with walls that are breathable. The homes also met the acoustic requirements of



buildings regulations (BRE 2001) and although its use in passive solar design has not been investigated Prof. T. Woolley felt that it was well suited for passive solar applications (Discussion forum; CAT (2006)

Hempcrete and Carbon Dioxide

The reduction of waste, the low embodied energy of the materials, the thermal performance and air-tight construction will all reduce the construction and running CO₂ debts of a house built using hempcrete for its walls.

There is also carbon sequestered from CO₂ in the atmosphere as hemp grows. For every tonne of hemp grown ~500kg of carbon is sequestered or ~1,800 kg of CO₂ (Pervais 2003). The embodied energy of hemp is 1.4 MJ tonne (BRE 2001, Cherrett 2005) which equates to ~0.112 kg of CO₂ per tonne (Calculated using CO₂ conversion factors quoted by Cherrett 2005 for UK farming = 0.0008 tonnes per MJ) meaning that approximately 1.8t of CO₂ is sequestered for every tonne of hemp hurds used. It is important to realize that this will be an overestimation as the calculations only involve the actual amount of carbon in hemp by weight and the embodied energy which appears very low. However it does not include the environmental costs of growing the hemp in monoculture, the NO₂ released from the land that is fertilized or the wider consequences of any herbicides if used. As NO₂ is a potent greenhouse gas therefore in terms of CO₂ equivalent CO₂e, the actual CO₂ saving in real terms will be much less for monoculture cultivation.

The recent French LCA uses French energy mix (~90% Nuclear) as well and although it accounts for the energy of manufacture of fertilizer doesn't include the emissions as above and fertilizer accounts of the ~60% energy used in farming (Boutin 2005), also note that all the figures for the binder in this LCA are from L'hoist provided data and presume high re-carbonation rates. Re-carbonation of lime is a difficult thing to assess accurately and is dependent on the lime binder being exposed to moisture and CO₂.

It is estimated that on average approximately 20-25% (Anon 2005) of the carbon dioxide is reabsorbed overtime. Opinion on this varies however and some say that 100% can be re-absorbed, due to impurities, lack of CO₂ and moisture 20-25% is generally realistic however is probably conservative with hemp and lime as this material is highly porous which would allow CO₂ and moisture access easily. It also takes about 1-5years to occur, however cement re-carbonates very slowly at a rate ~2% every 100 years. Thus for the different lime based binder a range of re-carbonation amounts will be presumed with the cement element of the binder no really reabsorbing any CO₂ during the 100year life of the building.

Further research is necessary in this area to accurately ascertain how much CO₂ is absorbed by the lime in the walls overtime.

Therefore, recalculating:



- 1m^3 of hempcrete uses 1000 litres of hemp hurds which weighs $\sim 100\text{kg}$, meaning that $\sim 180\text{kg}$ of CO_2 dioxide will be locked up per 1m^3 of wall in the hemp shiv.
- Lime used however has a wide range of embodied energy figures, from the ICE database 0.2 to 9MJ/kg, however the mean is 5.3MJ/kg and meaningful range is 4-9MJ/kg.

When calculating the total CO_2 emissions range from the CO_2 burnt from lime must be included as well as the CO_2 from embodied energy, all lime releases about $0.48\text{kgCO}_2/\text{kg}$ when burnt from the limestone.

For 5.3MJ/Kg ICE gives $0.74\text{kgCO}_2/\text{Kg}$ overall and this includes $0.48\text{kgCO}_2/\text{kg}$ from the limestone and thus $0.26\text{KgCO}_2/\text{Kg}$ from the 5.3MJ of energy used in the production process. Given the range of Embodied Energies for lime is 4-9MJ/kg, this gives a range of CO_2 emissions of $0.196 - 0.45\text{ KgCO}_2/\text{kg}$ for the embodied energy and thus overall a range of $0.676-0.93\text{KgCO}_2/\text{kg}$ before any re-carbonation has occurred. This means that anywhere between $676\text{ kg} - 930\text{kg}$ (mean $\sim 740\text{ kg}$) of CO_2 are released per tonne of lime produced (personal calc using Bath (2008)). Limetec's product contains $\sim 15-20\%$ cement which from the ICE database has an average of 0.83KgCO_2 per tonne and is thus reasonable equivalent to the lime in current production methods. Of note however cement embodied energy is hard to reduce further whereas lime can be produced from biomass kilns.

- $\sim 200\text{ kg}$ of lime will be used in 1m^3 of hempcrete
- meaning a range of $\sim 135\text{ kg} - 186\text{ kg}$ of CO_2 will be released into the atmosphere from the lime used to make a m^3 hempcrete (mean 148kg CO_2).
- Every kg of the lime will then re-absorb a certain ($\sim 25-75\%$) amount of CO_2 over time of the $0.48\text{kgCO}_2/\text{kg}$ burnt of during burning. This equates to a range of $0.12\text{kgCO}_2/\text{kg}$ to $0.36\text{KgCO}_2/\text{kg}$. Therefore for a m^3 of hempcrete (200kg of lime) this gives a range of CO_2 re-absorption $24-72\text{KgCO}_2/\text{kg}$ over time. For the Limetec binder this will be less by $15-20\%$ due to the cement content.
- Therefore overall the CO_2 emissions from the lime in a m^3 of hempcrete could be anywhere from 63kg ($135-72\text{kg}$) to 162kg ($186-24\text{kg}$).
- This then means that anywhere from 117kg to 18kg of CO_2 are sequestered into a m^3 of hempcrete depending on the embodied energy of the binder and the re-carbonation of the lime. These again are likely to be overestimates unless the hemp is grown organically.
- In a standard wall there is also the plaster and render to consider. Lime has a density of $\sim 1500\text{kg} / \text{m}^3$ therefore a m^2 of 20mm of lime plaster weighs $\sim 30\text{kg}$ which adds another $\sim 9.5-24\text{kgCO}_2$ of emissions per m^2 of wall if lime is used.
- Therefore, overall, for a standard 300 mm hempcrete wall every metre square (0.3m^3 of hempcrete) potentially locks up $\sim (117\text{kg} \times 0.3) - 9.5\text{kg} = 107.5\text{ kg}$ of CO_2 or emits $\sim ((-18\text{kg} \times 0.3) + 24\text{kg}) = 18.6\text{kg}$ of CO_2 , depending on the lime figures used.
- standard cavity wall constructions emit $100-220\text{ kg}$ of CO_2 per m^2 (Ian Pritchett CAT (2006), personal calc using Bath (2006)).



This emphasizes the crucial aspect of reducing the embodied energy of the lime to a minimum or using another binder with a lower embodied energy (e.g. **Clay**) to remove CO₂ from the atmosphere. These calculations don't take into account the CO₂ emissions from construction.

There are however potential CO₂ savings in running hempcrete homes, due to its good thermal performance, which significantly reduced the heating requirements of a home in Haverhill. The type of binder will influence the thermal performance of the walls and this influence is under further investigation.

Due to the farming aspects mentioned above and the uncertainties in the embodied energies further research is necessary in this area to ascertain a true picture of how CO₂ or CO₂e is locked up by using hempcrete, although if the hemp is grown organically and the binder is changed to clay this could potentially be ~180kg per m³ used. This could be a reasonably large sequestration of carbon especially if hemp and binder insulating plasters are utilized for renovations works.

Potential Market for Hempcrete

Although there is currently no market for hempcrete in the UK, interest is growing (Ansells Breweries have commissioned and had built a hempcrete building) and the French market has grown by 400% in the last 10 years. The costs of construction are low and there is proven example of performance in the Haverhill project which was acceptable to the local planning office in keeping with 2002 building regulations. The WISE building at CAT is being built using Hempcrete as an external skin (CAT (2006) Pat Borer 2007).

The size of the market is uncertain and could range from just a few environmental builders to larger developments, especially as it has a possible short construction time, it reduces waste and there is both increasing demand and legislation for environmental buildings. Add in the health benefits of breathable walls and the fact that carbon is stored in the walls, and it seems that the potential for hempcrete used in this style of construction could be considerable. The logistics of using hempcrete and the build period (Feb-Sept) are however unattractive.

Assessing this potential with a market research tool incorporating the attitudes and perceived desirability of hempcrete to the final consumer, the contractor, the processor and the farmer is beyond the scope of this lecture although is an area of research that is necessary. The 6000 tonnes of hurds used a year in France could build ~750 Haverhill style homes. In France the number of new buildings isn't as high as a proportion of the hurds are used to insulate old stone buildings in Northern France with an internal 50mm hempcrete covering. Anecdotally this technique is very successful although I couldn't find any published data on the technique beyond advertising.





References:

ADAS 2005; UK Flax and Hemp production: The impact of changes in support measures on the competitiveness and future potential of UK fibre production and industrial use; Report compiled by ADAS Centre for Sustainable Crop Management for DEFRA available at www.defra.gov.uk: accessed FEB 2006.

Ainsworth D. 2005, Achievement of the Millennium Development Goals requires the conservation and sustainable use of biological diversity: Press release: CONVENTION ON BIOLOGICAL DIVERSITY: www.biodiv.org/doc/statements/mdg-2005-en.pdf. Accessed Dec 2005.

Allsop M 2001, INCINERATION AND HUMAN HEALTH
State of Knowledge of the Impacts of Waste Incinerators on Human Health.
Environ Sci Pollut Res Int. 2001;8(2):141-5

Angelova V. 2004, Bio-accumulation and distribution of heavy metals in fibre crops (flax, cotton and hemp); Industrial Crops and Products 19 (2004) 197–205.

ANON 2000, What exactly is a "dry hydrate"?; House Magazine Spring 2000, www.wealddown.co.uk/Magazine/magazine%20march%2000%20dry%20hydrate.htm; Accessed Feb 2006.

Anon 2000a, Environment, Assessing the Impact, Quarrying Today August 2000

ARDI 2000, Agri-food Research and Development Initiative (ARDI);
DEVELOPMENT OF HEMP FOOD PRODUCTS AND PROCESSES
<http://www.gov.mb.ca/agriculture/research/ardi/projects/98-209.html> accessed Dec 2005.

Ball A. 2002; Agricultural influences on carbon emissions and sequestration.
UK Organic Research 2002: Proceedings of the COR Conference, 26-28th
March 2002, Aberystwyth, pp. 247-249.

Ball P. 2002; Sugar makes plastic biodegradable;
<http://shop.store.yahoo.com/annieappleseedproject/sugmakplasbi.html>: Accessed
Feb 2006.

BHF 2004, Diet, Chapter 5, British Heart Foundation Statistics Database: 2004
www.heartstats.org Accessed Dec. 2005

BHF 2004a, Economic costs, Chapter 13, British Heart Foundation Statistics
Database: 2004 www.heartstats.org Accessed Dec. 2005

Biofuels 2002, Biofuels for Sustainable Transport
<http://www.biofuels.fsnet.co.uk/sustain.htm>, Accessed Feb 2006.

Blackburn K. 2004, Feasibility of Hemp Textile Production in the UK, Bioregional
development group, www.bioregional.com; Accessed Dec 2005.



- Bouby L. 2002, Le chanvre (*Cannabis sativa* L.): une plante cultivée à la fin de l'âge du Fer en France du Sud-Ouest ? *C. R. Palevol* 1 (2002) 89–95. ^ 2002 Académie des sciences / Éditions scientifiques et médicales Elsevier SAS
- Bouguerra A. 1998; EFFECT OF MICROSTRUCTURE ON THE MECHANICAL AND THERMAL PROPERTIES OF LIGHTWEIGHT CONCRETE PREPARED FROM CLAY, CEMENT, AND WOOD AGGREGATES; *Cement and Concrete Research*, Vol. 28, No. 8, pp. 1179–1190, 1998
- Boutin 2006 ETUDE DES CARACTERISTIQUES ENVIRONNEMENTALES DU CHANVRE PAR L'ANALYSE DE SON CYCLE DE VIE ; MINISTERE DE L'AGRICULTURE ET DE LA PECHE ; *Référence MAP 04 B1 05 01 Sept 2006*
- Bowyer J.L. 2001, Industrial Hemp (*Cannabis sativa* L.) as a Papermaking Raw Material in Minnesota: Technical, Economic, and Environmental Considerations,
- Bowyer J.L. 2004, TREE-FREE PAPER – WHEN IS IT GOOD FOR THE ENVIRONMENT? www.dovetailing.org; accessed Feb 2006.
- BRE 2001; Final Report on the Construction of the Hemp Houses at Haverhill, Suffolk, Client report number 209-717 Rev.1. Edited by Tim Yates. 2002.
- BRE 2003; Thermographic Inspection of the Masonry and Hemp Homes- Haverhill, Suffolk: Client Report Number 212020.
- British Horse Society (BHS 2005); Advise on Horse bedding, The British Horse Society Welfare Department 2005. www.bhs.org.uk: Accessed Feb 2006.
- Bruce D.M. 2001, Stripping of Leaves and Flower Heads to improve the Harvesting of Fibre Hemp, *J. agric. Engng Res.*, (2001) 78 (1), 43}50
- Bruce D.M. 2005, Drying of Hemp for Long Fibre Production; *Biosystems Engineering* (2005) doi:10.1016/j.biosystemseng.2005.03.002: Article in Press: Available on-line <http://www.sciencedirect.com> ; December 2005.
- Better Regulations Task Force (BRTF) 2000; Environmental Regulations and Farmers
- Blade S. 1998; Industrial Hemp in Alberta Alberta Hemp Symposia Proceedings, 1998, <http://www1.agric.gov.ab.ca>. Accessed Dec 2005.
- Caleb (May 1998), Assessment of Potential for the Saving of Carbon Dioxide Emissions in European Building Stock, <http://www.eurima.org/downloads/caleb1.pdf>, Accessed Jan'05
- Callaway J. 2002; Hemp as Food at High Latitudes, *Journal of Industrial Hemp*, Vol. 7(1) 2002



Callaway J. 2004; Hempseed as a nutritional resource: An overview; *Euphytica* 140: 65–72, 2004.

Callaway J. 2005. Efficacy of dietary hempseed oil in patients with atopic dermatitis: *Journal of Dermatological Treatment*. 2005; 16: 87–94

Charest N. 1998, Industrial Hemp: Markets, The Next Challenge, Alberta Hemp Symposia Proceedings;
[http://www1.agric.gov.ab.ca/\\$department/deptdocs.nsf/all/opp551?opendocument](http://www1.agric.gov.ab.ca/$department/deptdocs.nsf/all/opp551?opendocument):
Accessed Dec 2005.

Cherrett N. 2005 Ecological Footprint and Water Analysis of Cotton, Hemp and Polyester, *Report prepared for and reviewed by BioRegional Development Group and World Wide Fund for Nature – Cymru*, ISBN 91 975238 2 8.

CIRIA 2004, Crops in Construction handbook, C614, November 2004.

Coltrain D. 2002, Biodiesel: Is It Worth Considering?; Risk and Profit Conference, Kansas State University, Holiday Inn, Manhattan, Kansas, August 15-16, 2002.

Cooper J 2003, The growth and development of industrial hemp (*Cannabis sativa*) in central western New South Wales; NSW Agriculture, Agricultural Research, Centre. <http://www.regional.org.au/au/asa/2003/c/11/cooper.htm> Accessed Dec 2005

David E. 1998, Indigo Print and Paperworks, Alberta Hemp Symposia Proceedings, 1998, <http://www1.agric.gov.ab.ca>. Accessed Dec 2005.

Davidovits, J. 1994, Global Warming Impact on the Cement and Aggregates Industry. *World Resource Review*, 6 (2) 263-78.
<http://www.geopolymer.org/library>, Accessed Dec 2005.

Davidovits, J. (2004) Up to 80% reduction of CO₂ Greenhouse Gas Emissions during Cement Manufacture. *Geopolymer Institute*.
<http://www.geopolymer.org/librar>; Accessed Feb 2006.

DEFRA, 2002. Action Plan to Develop Organic Food and Farming in England. (<http://www.defra.gov.uk/farm/organic/actionplan/index.htm>).

DEFRA 2003a, Climate Change Impacts & Adaptations Research Programme (CC03)
Project Summaries Report 1987 – 2003.
www.defra.gov.uk/environment/climatechange. Accessed Feb 2006.

DEFRA 2003, AN ASSESSMENT OF THE ENVIRONMENTAL IMPACTS OF ORGANIC FARMING: project OF0405.

DEFRA 2004, Farming quick statistics;
<http://statistics.defra.gov.uk/esg/quick/agri.asp> accessed Feb 06.



DEFRA 2004b, Energy Efficiency: the Government's Plan for Action, April 2004

DEFRA 2005, Environmental Stewardship: Look after your land and be rewarded; www.defra.gov.uk, es-promotional-booklet.pdf. accessed Dec 2005.

DEFRA 2005a, DEPARTMENT FOR ENVIRONMENT, FOOD & RURAL AFFAIRS HEALTH & SAFETY EXECUTIVE, A Guide to Pesticide Regulation in the UK and the role of The Advisory Committee On Pesticides, ACP 19 (311/2005)

DEFRA 2005b, Pesticide poisoning of animals in 2004; Investigations of suspected incidents in the United Kingdom: pdf. Available; www.pesticides.gov.uk; Accessed Feb 06

DEFRA 2005c, Use of agricultural crops (plant and animal) in construction, DEFRA project code: NF 0552

DEFRA 2005d, Review of the UK Insulation Sector Supply Chain; Dec 2005, ref. P01057

Demirbogia R. 2005, Thermo-mechanical properties of concrete containing high-volume mineral admixtures; Building and Environment in-press.

Der-Petrossian B. 2000, Construction and Environment – Improving energy efficiency, Building Issues vol. 10 number 2: 1-21.
<http://www2.hdm.lth.se/bi/report/frame.htm> accessed April 09

Department of the Environment (DOE 2001), Transport and the Regions [DETR] Guidelines for Company Reporting on Greenhouse Gas Emissions, 2001

Dornburg V. 2005, Economic and greenhouse gas emission analysis of bioenergy production using multi-product crops—case studies for the Netherlands and Poland, Biomass and Bioenergy 28 (2005) 454–474

Dresboll D.B. 2005, Structural changes of plant residues during decomposition in a compost environment; Bioresource Technology. In- press at time of writing.

Dreyer J. 2002, Comparison of Enzymatically Separated Hemp and Nettle Fibre to Chemically Separated and Steam Exploded Hemp Fibre; Journal of Industrial Hemp, Vol. 7(1) 2002

DTI 2003, Our Energy Future – creating a low carbon economy.

EERE 2005, US department of energy: Passive solar design.
<http://www.eere.energy.gov/buildings/info/design/integratedbuilding/passive.html>.
Accessed July 2005

EIA 2004, Energy Information Administration, International Energy Annual 2001. DOE/EIA 2001, <http://www.eia.doe.gov/iea/2010-2025>: EIA System for the analysis of energy markets (2004).



Ellison G. 2000; MAFF report NF0390; THE USE OF NATURAL FIBRES IN NONWOVEN STRUCTURES FOR APPLICATIONS AS AUTOMOTIVE COMPONENT SUBSTRATES. Feb 2000.

Embodied Energy pdf. www.vuw.ac.nz/cbpr/documents/pdfs/ee-coefficients.pdf
Accessed Feb 2006.

FAO 1987, TECHNICAL AND ECONOMIC ASPECTS OF USING WOOD FUELS IN RURAL INDUSTRIES;
http://www.fao.org/documents/show_cdr.asp?url_file=/DOCREP/004/AB780E/AB780E06.htm Accessed Feb 2006.

Ferrel J. 2002, "Biodiesel–Clean, Green Diesel Fuel" Produced for the U.S. Department of Energy (DOE) by the National Renewable Energy Laboratory, a DOE national laboratory DOE/GO-102001-1449 Revised February 2002.
<http://www.nrel.gov/docs/fy01osti/30882.pdf> Accessed Feb'06.

Fraangie P. 1997; Cascading Renewable source Hemp and Reed; Industrial crops and products; 6 (1997) 201-12.

Galloway, J.N.2003: The nitrogen cascade. *BioScience* 53: 1-16.

Gauca C (1987). Influence of Chemical Fertilisers on Stem and Fibre Yields of Monoecious Hemp on the Moldavian Plateau. *Cerecetari Agronomice in Moldova*. 20:82-84. In: *Field Crop Abstracts* 41, 5559.

Gilbertson H. 2004, Insulation materials from flax fibresCrop: www.baltic-network.de/index.php?page6. Accessed Feb 2006.

Greenspec 2005, Materials – Insulations Compared
<http://www.greenspec.co.uk/html/design/materials/insulation.html>: accessed Dec 2005.

Gupta T. 2003, Environmental, Economic and Societal Considerations in Engineering Applications; *Environmental Informatics Archives*, Volume 1 (2003), 220-227

Harasztya A. & Jakoby I. (1968). Effects of Trace Elements on the Harl Formation of Hemp. *Acta Biol. Debrecina* 6:53-64. *Field Crop Abstracts* 23, 3915.

Hautala M. 2004, Use of hemp and flax in composite manufacture: a search for new production methods, *Composites: Part A* 35 (2004) 11–16

Heneas Centre 2005, Flax and Hemp Project, University of Wales, Bangor, Gwynedd. UK

Hessler L. 1947, The Effect of Fertilisers on the Chemical Composition and Quality of Dew Retted Hemp Fibre. *J. Amer. Soc. Agron.* 39. 812 6. *Field Crop Abstracts* 1,582.



Hole D.C. 2005, Does organic farming benefit biodiversity? *Biological Conservation* 122 (2005) 113–130.

Howard N. 2000, Sustainable construction – The Data, BRE 2000, CR258/99

IENICA 2004, Agronomy Guide Generic guidelines on the agronomy of selected industrial crops; August 2004

IENICA 1999, REPORT FROM THE STATE OF FRANCE FORMING PART OF THE IENICA PROJECT

IENICA 1999a, REPORT FROM THE STATE OF THE UNITED KINGDOM FORMING PART OF THE IENICA PROJECT

IENICA 2004a, REPORT FROM THE STATE OF THE UNITED KINGDOM FORMING PART OF THE IENICA PROJECT, 2004 Update.

IENICA 2003, report from the state of France forming part of the IENICA project December 2003.

Industrial Hemp Investigative and Advisory Task Force Report, Illinois (IHIATF, Illinois 1999):http://www.globalhemp.com/Media/Magazines/Global_Hemp_Magazine/2000/January/il_task_force_report.shtml, Accessed Dec 2005.

Innvista 2005, Hemp Harvesting;
<http://www.innvista.com/health/foods/hemp/harvest.htm>; Accessed Feb 2006.

Jaakkola M.S. 2003; Respiratory health effects of molds. Presented at: annual conference of the American Thoracic Society; May 19, 2003; Seattle, Wash.

Jakobey I.1968; Effects of Microelements and Fertilisers on the Fineness of Hemp. Rostnoyenyek Kompolt 1968, 13-20. In: *Field Crop Abstracts*, 22.

Jones, A.P. 1999a; Indoor air quality and health, *Atmospheric Environment* 33 (1999) 4535-4564

Joshi S. 2004, Are natural fiber composites environmentally superior to glass fiber reinforced composites?; *Composites: Part A* 35 (2004) 371–376

Kahn M. 2002, Factors affecting the thermal properties of concrete and applicability of its prediction models; *Building and Environment* 37 (2002) 607 – 614

Karus M. 2005, European hemp industry 2001 till 2004: Cultivation, raw materials, products and trends; European Industrial Hemp Association (EIHA): www.eiha.org, Accessed Feb 2006.

Karus M. 2002, Natural Fibres in the European Automotive Industry, *Journal of Industrial Hemp*, Vol. 7(1) 2002



Karus 2000, Study on Markets and Price Situation of Natural Fibres (Germany and EU); Sponsor ID : 99NR163; Nova Institute March 2000. " www.nova-institut.de"

Kloberdanz J. Producer Experience with Growing Hemp; Alberta Hemp Symposia Proceedings, 1998, <http://www1.agric.gov.ab.ca>. Accessed Dec 2005.

Koivula M. 2004, Emissions from thermal insulations—part 2: evaluation of emissions from organic and inorganic insulations; Building and Environment 40 (2005) 803–814.

Krauss A. 2004, Balanced fertilization, the key to improve fertilizer use efficiency, Presented at the AFA 10th International Annual Conference Cairo, Egypt 20-22 January 2004: Available on-line: <http://www.ipipotash.org>: Accessed Feb 06.

Kristensen, E.S.1995, A simple model for estimation of atmospherically-derived nitrogen in grass-clover systems. *Biol. Agric. Hort.* 12, 263-276.

Kruger K. 2000, Several years investigation on hemp Cultivation in Brandenburg. BIORESOURCE HEMP 2000, Wolfsburg 13 -16 September 2000. www.nova-institut.de

Lampkin, N. 1990. "Organic Farming". Farming Press Books. Ipswich, UK.

LeVan S. 1990, The role of boron in flame-retardant treatment; Hamel, Margaret, ed. 1st International conference on wood protection with diffusible preservatives: Proceedings 47355; 1990 November 28–30; Nashville, TN. Madison, WI: Forest Products Research Society; 1990:39-41.

Liberalato D. 2000; Prospect of Hemp Utilisation in the European Textile Industry.

Lingard J 2002, Agricultural Subsidies and Environmental Change, Encyclopedia of Global Environmental Change. Copyright @ 2002 John Wiley & Sons, Ltd

Lisson, S.N. 1995. Tasmanian hemp research. *Journal of the International Hemp Association* 2(2): 82-85.

Lotz, L. 1991. "Reduction of growth and reproduction of *Cyperus esculentus* by specific crops," *Weed Research*. 31: 153-160.

Mailloux N, 2003, Pesticides and the Kyoto Protocol:
<http://www.pesticidefree.ca/kyoto.htm> Accessed Feb 2006.

MAFF 2000, Project NF0307 - HEMP FOR EUROPE MANUFACTURING AND PRODUCTION SYSTEMS.

MAFF 2001a, Project PN0907 - Potential exposure of birds to treated seeds, MAFF Environmental, R&D Newsletter, pdf. available
<http://www.maff.gov.uk/maffhome.htm>; Accessed: Dec 2005



MAFF 2001b, Project OF0182 - Energy use in organic farming systems, MAFF Environmental, R&D Newsletter, pdf. available
<http://www.maff.gov.uk/maffhome.htm>; Accessed: Dec 2005

Maskell, and C.A. Johnson (eds.)]. Cambridge University Press, Cambridge, United Kingdom and New York, NY, USA, 881pp.

May N. 1998, The Ecology of Lime:
http://naturalbuildingproductscouk.ntitemp.com/ecology_lime.htm; Accessed Feb 2006.

McGinness S. 1999: The Climate Change Levy: House of Commons Library Research Paper 99/93.

[Mccook A. 2005.](#) The Banned Pesticide in Our Soil, The scientist, Volume 20 | Issue 1 | Page 40: <http://www.the-scientist.com/article/display/18858>: Accessed Feb2006.

Mcnamara P 2005; Property Week 14-10-05 pp84-86

McPartland, J.M. 1999. A survey of hemp diseases and pests. In: Ranalli, P. (ed.). Advances in Hemp Research. New York: Food Products Press, pp. 109-131.

McPartland J.M. 2002, Epidemiology of the Hemp Borer, *Grapholita delineana* Walker (Lepidoptera: Oleuthreutidae), a Pest of *Cannabis sativa* L. Journal of Industrial Hemp, Vol. 7(1) 2002

Mediavilla V.2001, Influence of the growth stage of industrial hemp on the yield formation in relation to certain fibre quality traits, Industrial Crops and Products 13 (2001) 49–56

Mendes N. 2001, MOISTURE CONTENT INFLUENCE ON THERMAL CONDUCTIVITY OF POROUS BUILDING MATERIALS; Seventh International IBPSA Conference, Rio de Janeiro, Brazil: August 13-15, 2001

Midmore P. & N. Lampkin. (1988). Organic Production as an Alternative to Set Aside. In Welsh Studies in Agricultural Economics. No.7, 57

Milia D. 2006, Exergy-based lumped simulation of complex systems: An interactive analysis tool; Energy 31 (2006) 100–111.

Mole, M, 1997. "Willingness to Pay for Hemp Based Products: Evidence from a Consumer Survey." Presentation at the Bioresource Hemp 97 Conference held in Frankfurt, Germany in February, 1997. Mr. Mole is with the Department of Community Development and Applied Economics at the University of Vermont

Montford, S. 1999. A comparison of the biodiversity friendliness of crops with special reference to hemp (*Cannabis sativa* L.) *Journal of the International Hemp Association* 6(2): 53-63



Motherhemp News 2002;

http://www.motherhemp.com/newsfull/06_march_02.html: Accessed Feb 2006.

MRC 1997, Fibrous Material in the Environment; A review of Asbestos and man made mineral fibres. ISBN 1 899110 17 8

Myers N. 2001, "The biotic crisis and the future of evolution" published in *Proc. Natl. Acad. Sci. USA*, Vol. 98, Issue 10, 5389-5392, May 8, 2001.

National Park Management Plan NPMP 2000: Economy, 26. Minerals. Pg 84-86.

Nelson R. 2000; Hemp Husbandry:

<http://www.rexresearch.com/hhusb/hh11stcr.htm>; accessed Dec. 2005

Newman G. 2005, ISONAT® Hemp Insulation: An assessment of the market potential of natural fibre insulation: Biofiber Industry Advancement Workshop Saskatoon, October 2005.

Nix J. 2004 Farm Management Pocket Book. 34th Edition 2004.

NFU 2006, About Agriculture

http://www.nfu.org.uk/intradoc/cgi/idc.cgi_isapi.dll?IdcService=GET_DOC_PAGE&Action=GetTemplatePage&Page=NFU_ABOUT_AG_PAGE: Accessed Feb 2006.

NOAA 2005, NOAA REVIEWS RECORD-SETTING 2005 ATLANTIC HURRICANE SEASON: <http://www.noaanews.noaa.gov/stories2005/s2540.htm>, Accessed Dec 2005.

NSIDC 2005b, State of the cryosphere, Ice shelves, <http://nsidc.org/sotc/iceshelves.html>, Accessed Dec 2005

Olsen JK, 2004. An information paper on industrial hemp (industrial cannabis). Department of Primary Industries and Fisheries, Queensland Government.

OMSH (One Million Sustainable Homes) 2006, Government code brings sustainability closer to home. www.org.uk/news/n-0000002363.asp. Accessed March 2006.

Papadopoulos A. 2005, State of the art in thermal insulation materials and aims for future developments: *Energy and Buildings* 37 (2005) 77–86.

Pasila A. 2004, The dry-line method in bast fibre Production, University of Helsinki Faculty of Agriculture and Forestry, Department of Agricultural Engineering and Household Technology

Paustian K, 2002, Agriculture and Greenhouse Gas Mitigation: Who, What, How, Where and When? Presented at Agricultural Outlook Forum 2002, Arlington, VA, Feb 21 2002; Available on-line:

<http://www.usda.gov/oce/waob/Archives/2002/speeches//Paustian.doc>. Accessed Feb 06.



Pervaiz M. 2003, Carbon storage potential in natural fiber Composites; Resources, Conservation and Recycling 39 (2003) 325_ 340

Peterson C 1998, Biodegradability, BOD5, COD and Toxicity of Biodiesel Fuels, <http://www.uidaho.edu/bioenergy/BiodieselEd/publication/04.pdf>, accessed Feb'05

Plotkin, Mark J., Medicine Quest, Penguin Books, 2001.

Pollard S. 2005, Biofuels – towards an integrated approach, FARM 29.12.05

Powlson, D. S. (2000). Tackling Nitrate from Agriculture. Soil Use and Management 16, 141.

Pretty J 2005, Farm costs and food miles: An assessment of the full cost of the UK weekly food basket. Elsevier.2005

Pretty J. 2001, THE REAL COSTS OF MODERN FARMING, Resurgence issue 205, <http://www.resurgence.org/resurgence/issues/pretty205.htm>; Accessed Feb 2006.

Pimental D. 2004; Environmental and economic costs of the application of pesticides primarily in the United States. <http://www.mp.wa.gov.au/jscott/ACE/ENVIRONMENTALANDECONOMICCOSTS.htm>; Accessed Dec 2005.

Pless P. 1998, Guide to Hemp Oil; Leson Enviromental consulting July 1998

[Rabenseifer](#) R 1997, Computer Model of the Apartment Building from the Panel System T06B, IBPSA Conference 1997. <http://www.ibpsa.org/proceedings/bs97/papers/P196.PDF> Accessed Feb 2006.

Randall Fortenbery T. 2001, Is Industrial Hemp Worth Further Study in the U.S.? A Survey of the Literature; University of Wisconsin-Madison; Staff Paper No. 443

Riddlestone S. 1995; Hemp for Textiles, Growing our own clothes, Bioregional Report.

Robson M. 2001, The agronomic and economic potential of break crops for ley/arable rotations in temperate organic agriculture. Sponsored by the UK ministry of Agriculture.

Rocco M. 2002, Borax; Boric Acid, and Borates <http://ipmofalaska.homestead.com/files/Borates.html>; Accessed Dec 2006.

Sankari H. 2000, Comparison of bast fibre yield and mechanical fibre properties of hemp (*Cannabis sativa* L.) cultivars, Industrial Crops and Products 11 (2000) 73–84.



Sayin C. 2005, Assessing of energy policies based on Turkish agriculture: current status and some implications; *Energy Policy* 33 (2005) 2361-73.

Schafer T, 2005. Effect of sowing date and plant density on the cell morphology of hemp (*Cannabis sativa* L.), *Industrial Crops and Products* in-press

Schafer Library 2005, Industrial hemp farming: History and practice; <http://www.druglibrary.org/schaffer/hemp/indust/INDHMPFR.HTM> accessed Feb 2006.

Schmidt A. 1996; Comparative Life Cycle Assessment of three insulation materials; DK energy and environment commissioned by rockwool manufacturer.

Scholz V. 2002, The growth productivity, and environmental impact of the cultivation of energy crops on sandy soil in Germany, *Biomass and Bioenergy* 23 (2002) 81 – 92

Schor J 2003 (47-49). *The Sustainable Planet: Solutions for the Twenty-first Century*.

Schultes RE, 1970. Random thoughts and queries on the botany of Cannabis. pp. 11-38. In RB Joyce and SH Curry (eds). *The botany and chemistry of Cannabis*. J & A Churchill, London, UK.

Seedtec 2005, *FIN-314 - Oil Seed Hemp Variety*, <http://www.terramax.sk.ca/hemp/hemp.html> accessed Feb 2006.

Select Committee on Environment, Food and Rural Affairs, 2003, Supplementary memorandum submitted by Greenenergy <http://www.publications.parliament.uk/pa/cm200203/cmselect/cmenvfru/929/929we10.htm> Accessed Dec 2005

Soil Association (2000). *Food and Farming Report*. Soil Association, Bristol.

Sheehan J. 1998, Life Cycle Inventory of Biodiesel and Petroleum Diesel for Use in an Urban Bus, U.S. Department of Agriculture and U.S. Department of Energy Final Report. <http://www.nrel.gov/docs/legosti/fy98/24089.pdf>. Accessed Feb'06

Small, E. 2002. Hemp: A new crop with new uses for North America. p. 284–326. In: J. Janick and A. Whipkey (eds.), *Trends in new crops and new uses*. ASHS Press, Alexandria, VA.

Soil Association (SA 2005), How organic farming delivers biodiversity benefits. <http://soilassociation.org>: Accessed Dec 2005

Soil Association (SA 2005b), Soil Association Information sheet Document: How does organic farming benefit wildlife? <http://soilassociation.org>: Accessed Dec 2005



- Soil Association (SA 2005c), Press release Biodiversity;
<http://www.soilassociation.org/web/sa/saweb.nsf>: Accessed Feb 2006
- Springdale Farming Group 2005, Agronomy Oil Hemp Crop;
http://www.york.ac.uk/org/cnap/oilcrop/cropsind/hemp_agro.htm: Accessed Dec 2005.
- Springdale Farming Group 2006, Hemp; <http://www.springdale-group.com/downloads/flyer/hemp.pdf> Accessed Feb 2006.
- Straube J.F. 2001; Indoor Air Quality, Healthy Buildings, and Breathing Walls, ASHRAE Transactions, vol 107, Pt 1.
- Struik P. 2000, Agronomy of fibre hemp (*Cannabis sativa* L.) in Europe, Industrial Crops and Products 11 (2000) 107–118.
- Suffolk Agricultural Association (SAA) 2006, "Reinvigorating Agriculture"
http://www.suffolkshow.co.uk/about_conferences_new.htm accessed Feb 2006.
- Sustainable Homes 1999; EMBODIED ENERGY IN RESIDENTIAL PROPERTY DEVELOPMENT; A Guide for Registered Social Landlords: PP3/99
- Tanneeru M 2005. It's official: 2005 hurricanes blew records away, CNN:
<http://www.cnn.com/2005/WEATHER/12/19/hurricane.season.ender/index.html>
Accessed Dec 2005.
- Tat M. E., PhD Thesis,
<http://www.me.iastate.edu/biodiesel/Technical%20Papers/Mustafa%20Intro.pdf>,
accessed Feb '06
- TCPA 2003, Building Sustainably: how to plan and construct new housing for the 21st century. October 2003
- Townsend, A.R. 2003: Human health effects of a changing global nitrogen cycle. Front. Ecol. Environ. 1(15): 240-246.
- Turpin B. 1997“sdg” ASHRAE Summer meeting, 28 June- 2 July
- Tzikopoulos A.F. 2005, Modeling energy efficiency of bioclimatic buildings, Energy and Buildings 37 (2005) 529–544.
- UNEP and UNFCCC 2002, Climate Change Information Sheet.
- US Borax 2000; Borax Decahydrate, Materials Safety Data Sheet.
- USDA 2000, U.S. Department of Agriculture 2000, Industrial Hemp in the United States: Status and Market Potential
- USDE 2005 United States Department of Energy: Lime:
<http://www.oit.doe.gov/e3handbook/l.shtml>; Accessed Feb 2006.



- Van dam J. 2000. OPTIMISATION OF METHODS OF FIBRE PREPARATION FROM AGRICULTURAL RAW MATERIALS;
www.ienica.net/fibresseminar/vandam.pdf, Accessed Feb 2006.
- van der Werf, H.M.G., 1994. Quality of hemp (*Cannabis sativa* L.) stems as a raw material for paper. *Ind. Crops Prod.* 2, 219–227.
- van der Werf H.M.G. 1997. The effect of plant density on light interception in hemp (*Cannabis sativa* L.) *Journal of the International Hemp Association* 4(1): 8-13.
- Vantresse V. 1998, INDUSTRIAL HEMP: GLOBAL OPERATIONS, LOCAL IMPLICATIONS; University of Kentucky, Department of Agricultural Economics.
- Valovirta I. 2002, Hemp as an insulation material in Wooden Houses: Session 11: Properties and Materials and Products; *Building Physics 2002 – 6TH Nordic Symposium*.
- Vindheim J. 2002, The History of Hemp in Norway; *Journal of Industrial Hemp*, Vol. 7(1) 2002.
- Vignon M. 1996, MORPHOLOGICAL CHARACTERIZATION OF STEAM EXPLODED HEMP FIBERS AND THEIR UTILIZATION IN POLYPROPYLENE-BASED COMPOSITES; *Bioresource Technok~ 58 (1996)* 203-215
- Vogl C. 2004, Comparing Hemp Seed Yields (*Cannabis sativa* L.) of an On-Farm Scientific Field Experiment to an On-Farm Agronomic Evaluation Under Organic Growing Condition in Lower Austria. *Journal of Industrial Hemp*, Vol. 9(1) 2004.
- Wassen M. J. 2005, Endangered species persist under phosphorous limitation; *Nature* vol 437, 547-50.
- Waste not, Want not 2002, A strategy for tackling the waste problem in England, Strategy Unit November 2002.
- Weightman R. 2005, Review and analysis of breeding and regulation of hemp and flax varieties available for growing in the UK, Final report for The Department for Environment Food and Rural affairs (DEFRA); Project NF053
- Wheeler B. D. 1991, Above-ground crop mass and species richness of the principle types of herbaceous rich-fen vegetation of lowland England and Wales. *J. Ecol.* 79, 285-301
- WHO 2002, The World Health Report, Reducing risks Promoting Healthy Life.
- Willerroider 2003, Roaming polar bears reveal Arctic role of pollutants, *Nature*, vol. 460, pg-5.
- Wilson A. 2005, Insulation Materials: Environmental Comparisons:
<http://www.buildinggreen.com/auth/article.cfm?fileName=040101a.xml> Accessed Feb 2006.



Winrock International India (WII) 2005, An Initiative for Performance Enhancement of Small-scale Lime Kilns in India; www.winrockindia.org. Accessed Feb 2006.

Woolley T. 2004, THE ROLE OF LOW IMPACT BUILDING MATERIALS IN SUSTAINABLE CONSTRUCTION: THE POTENTIAL FOR HEMP; www.sustainablesettlement.co.za/event/SBE2004/papers/SB014.pdf+breathing+walls+hemp&hl=en: Accessed Dec 2005.

WRAP 2004, Market share of recycled content in construction procurement: Summary

Wright J. 1995, Organic cultivation of hemp Section 1.4; Riddlestone S. 1995; Hemp for Textiles, Growing our own clothes, Bioregional Report.

WWF 1994, FREIGHT TRANSPORT, LOGISTICS AND SUSTAINABLE DEVELOPMENT. Prepared by Eco-Logica Ltd

WWF 2004, Living Planet Report 2004.

XC02 2005; Insulation for Sustainability– A Guide; <http://www.insulation.kingspan.com/newdiv/pdf/lfs%20Summary.pdf> Accessed Feb 2006.

Yu L.L. 2004, Antioxidant properties of cold-pressed black caraway, carrot, cranberry, and hemp seed oils, Food Chemistry, Volume 91, Issue 4, August 2005, Pages 723-729

Bibliography:

Building with Lime: A practical introduction, Stafford Holmes and Micheal Wingate; Revised Edition 2002, ITDG Publishing ISBN 1 85339 547 1